



Cite this: *Nanoscale*, 2016, **8**, 14379

Received 19th May 2016,
 Accepted 11th July 2016

DOI: 10.1039/c6nr04082a

www.rsc.org/nanoscale

Single step deposition of an interacting layer of a perovskite matrix with embedded quantum dots†

Thi Tuyen Ngo,^a Isaac Suarez,^b Rafael S. Sanchez,^a Juan P. Martinez-Pastor^b and Ivan Mora-Sero*^a

Hybrid lead halide perovskite (PS) derivatives have emerged as very promising materials for the development of optoelectronic devices in the last few years. At the same time, inorganic nanocrystals with quantum confinement (QDs) possess unique properties that make them suitable materials for the development of photovoltaics, imaging and lighting applications, among others. In this work, we report on a new methodology for the deposition of high quality, large grain size and pinhole free PS films ($\text{CH}_3\text{NH}_3\text{PbI}_3$) with embedded PbS and PbS/CdS core/shell Quantum Dots (QDs). The strong interaction between both semiconductors is revealed by the formation of an exciplex state, which is monitored by photoluminescence and electroluminescence experiments. The radiative exciplex relaxation is centered in the near infrared region (NIR), ≈ 1200 nm, which corresponds to lower energies than the corresponding band gap of both perovskite (PS) and QDs. Our approach allows the fabrication of multi-wavelength light emitting diodes (LEDs) based on a PS matrix with embedded QDs, which show considerably low turn-on potentials. The presence of the exciplex state of PS and QDs opens up a broad range of possibilities with important implications in both LEDs and solar cells.

Nowadays, the research focused on the development and applicability of hybrid lead halide perovskite (PS) materials probably constitutes the hottest topic in the photovoltaics field due to several reasons. Firstly, certified photoconversion efficiencies as high as 22.1% have been reported so far.¹ Moreover, the impressive rise in the conversion efficiencies has been reached only few years after the first reports on PS based liquid electrolyte solar cells in 2009.² Very importantly, it has been demonstrated that PS shows reduced non-radiative recombination pathways; this fact has significantly contributed to reach high photoconversion efficiencies.^{3,4} Additionally, the

application of PS derivatives for the development of light emitting devices,⁵ as LEDs,^{6–8} light amplifiers⁹ or lasers,^{10–12} has already been demonstrated, which is a consequence of the outstanding properties of these materials. It is worth pointing out that PS can be prepared from solution methods at low processing temperatures and, consequently, using low cost fabrication techniques. Furthermore, PS can be easily combined with other materials such as colloidal Quantum Dots (QDs),^{13,14} which can induce interesting synergies, thus giving rise to new properties or phenomena that do not exist for the single materials.

Colloidal QDs constitute a very interesting family of nanomaterials that have been extensively studied for optoelectronic applications during the last two decades due to their size-tunable bandgap, relatively facile synthesis, high monodispersity, and the possibility of being processed in solution.^{15–18} Despite the high potentiality of developing advanced optoelectronic systems by exploiting the combination of PS and QDs, there are only a few examples in the literature reporting on these issues; PbS QDs combined with PS have been the most general system studied so far. Particularly, precedents in the literature report on the utilization of PS as a capping agent of QDs, thus providing QD/PS core/shell structures,^{19–21} which have shown outstanding efficiencies, close to 9%, in a colloidal QD solar cell configuration.¹⁹ PbS QDs have been deposited on perovskite layers for photovoltaic applications, which enhances the light harvesting at IR wavelengths and therefore, the photo-generated short-circuit current (J_{sc}).^{22,23} However a more intimate interaction between PS and QDs has been obtained by the preparation of layers that consist of a PS matrix with embedded QDs using a two-step spin coating method.¹³ This approach has an enormous potentiality for the development of different optoelectronic devices. Highly efficient QD based near-infrared light-emitting diodes have been obtained by combining a PS matrix with PbS QDs with good lattice matching and forming a type I junction.²⁴ In addition, PbS QDs have also been used as efficient seeds for the preparation of high-performance planar heterojunction perovskite solar cells.²⁵ We have recently analyzed the interaction between PS and

^aInstitute of Advanced Materials (INAM), Universitat Jaume I, 12006 Castelló, Spain.
 E-mail: sero@uji.es

^bUMDO, Instituto de Ciencia de los Materiales, Universidad de Valencia, 46071 Valencia, Spain

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c6nr04082a

PbS/CdS core-shell QD bilayers that form a type II junction.¹⁴ More specifically, we reported on the identification of an exciplex emission that results from the strong interaction between both semiconductor films, by means of optical pumping and electrical injection at energies lower than the bandgap of the single materials. As a continuation of our previous work, we envisaged that this effect could be much more pronounced if the QDs were inserted into the PS films instead of stacking layers of the corresponding single materials. Therefore, in the present paper we propose a novel one step spin coating method to produce a nanocomposite that consists of either core PbS or core/shell PbS/CdS QDs embedded into a PS matrix. This method permits to obtain very uniform PS-QD layers, with a significantly larger PS grain size, compared to bare PS (reference sample), which clearly exhibits exciplex emission.

PbS/CdS core/shell QDs were generally synthesized using oleic acid (OA) that controls the dimension of QDs and prevents their aggregation. However OA-capped QDs are not soluble in dimethylformamide (DMF), which is the solvent commonly employed to dissolve the PS precursor, and therefore a ligand exchange treatment becomes necessary to overcome this solubility limitation. Fig. 1a shows the ligand exchange processes. Core/shell PbS/CdS QDs capped with OA ligands were originally dispersed in octane, and mixed with a DMF solution containing PS precursors (PbI₂ and CH₃NH₃I). In this step, two separated phases were detected: QDs dispersed in octane on the top and PS dissolved in DMF at the bottom (Bottle 1). After stirring the mixed solution, OA is replaced by a CH₃NH₃PbI₃ PS capping agent and QDs were transferred into the DMF phase with perovskite precursors (dark phase, Bottle 2). QDs with PS capping agent (PS-capped QDs) were precipitated with toluene, dried and finally dispersed in a solution containing the PS precursors (PS-QD solution, Bottle 3) that will be used for the spin coating deposition of the PS with embedded QD films (see the details in the experimental part of the ESI†). The absorbance and photoluminescence (PL) in the solution of PS-capped QDs are red shifted (see Fig. 1b and

S1a†) and the PL quantum yield is significantly reduced after ligand exchange, from 18% to 0.9% (see Fig. S1b†).

Fig. 1b shows the PL spectra of the QD solutions before (OA capped) and after ligand exchange (PS capped). The PL peak after ligand exchange was red shifted depending on the QD size, being 150 nm for QDs of 2.3 nm in diameter (from 812 nm to 962 nm, Fig. 1b and Fig. S1c†) and 83 nm for QDs of 3 nm in diameter (from 893 nm to 976 nm, Fig. S1d†), thus indicating that this effect is more significant for the smaller sized QDs, which is in good correlation with previous reports.²⁰ PS capping allows the wave function to spread out of QDs, thus reducing the quantum confinement that provokes the strong red-shift. The PL emission of the QD/PS nanocrystals dispersed in the PS solution (PS-QD solution) did not vary compared to that resulting from dispersing QD/PS in DMF, see Fig. 1b, S1c and S1d.† This fact indicates that the PS shell does not dissociate into the corresponding precursors or does not suffer from chemical variations after being dispersed in DMF, which demonstrates the robustness of the PS shell. The QY of the PS-QD solution was calculated as a function of QD concentration, which decreases linearly from 1.6% to 1% when the QD concentration was increased from 200 to 400 mg ml⁻¹ (Fig. S2†).

PS and PS-QD films were spin coated onto compact TiO₂ at 9000 rpm from the PS and PS-QD solutions, respectively, inside a glove box. The films were annealed at 65 °C for 1 minute and subsequently at 100 °C for 2 minutes. Very homogenous, pinhole free morphology was obtained for both PS and PS-QD films (Fig. 2a and b, respectively). The introduction of QDs in the solution containing the perovskite precursors has a dramatic effect on the grain size, which is increased by 4–5 fold. These results point to the significant role of the QDs in the nucleation of the PS crystals, as has been recently reported.²⁵ The increase of PS grain size produced a slight red shift, around 4 nm in the PS emission (Fig. S3†).²⁶ Very interestingly, crystal grains with a size similar to the layer thickness are obtained (see Fig. 2c and d), which is a crucial

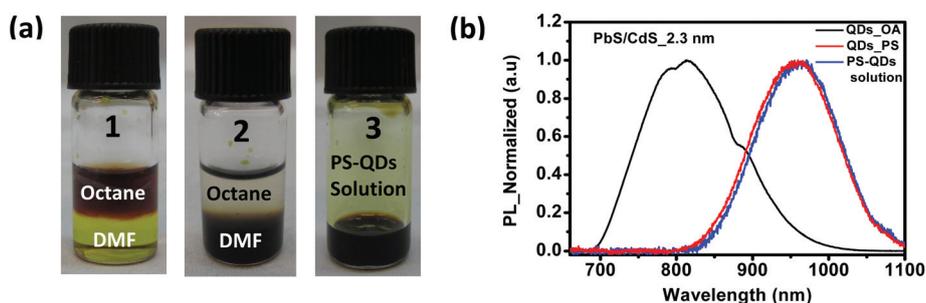


Fig. 1 (a) Pictures of the different phases of a QD ligand exchange process. Bottle 1: two phase solution formed by DMF with perovskite precursors at the bottom and PbS/CdS core/shell QDs capped with OA dispersed in octane on the top. Bottle 2: after 30 minutes stirring, the QDs were transferred into DMF since OA was exchanged by a PS shell. Bottle 3: QDs with PS capping were precipitated with toluene, dried and finally dispersed in a DMF solution containing PS precursors (PbI₂ and CH₃NH₃I, 1:1 molar ratio); this solution is used for the deposition of perovskite layers with embedded QDs. (b) Photoluminescence spectra of PbS/CdS QDs in solution before (OA capped) and after ligand exchange (PS capped) and the final PS-QD solutions ($\lambda_{\text{excitation}} = 650$ nm).

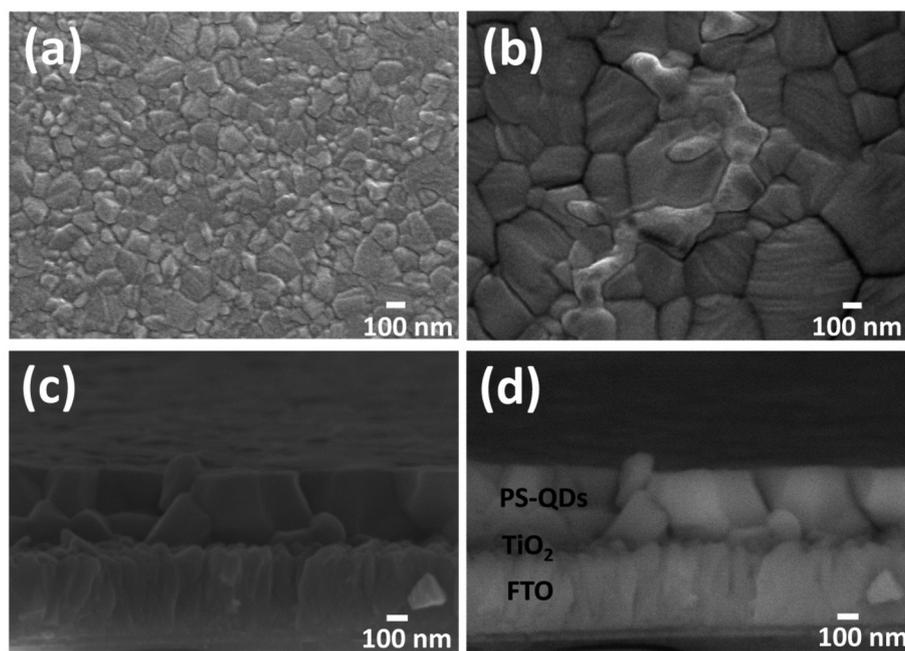


Fig. 2 SEM secondary electron images of the top view of PS films (a) without and (b) with PbS/CdS core/shell 2.3 nm QDs with the concentration of 300 mg ml^{-1} . Cross sectional image of (b) sample using (c) secondary electrons and (d) backscattered electrons that allow a clearer distinction between the different layers.

aspect for obtaining high performance optoelectronic devices. The presence of QDs also produces an increase of the film thickness (see Fig. S4†), from 210 nm (PS film without QDs) to 365 and 420 nm, when QDs are dispersed in PS solutions with concentrations of 300 and 400 mg ml^{-1} , respectively. Independently of the thickness, very homogeneous films are obtained under different conditions by exploiting our novel preparation methodology.

Fig. 3 shows that PS layers with embedded QDs exhibit the PL emission band ascribed to the exciton recombination in the PS, but no additional QD contribution is observed within the comprised spectral range (Fig. 3a). However, these compo-

site films exhibit a strong exciplex emission ($\approx 1.02 \text{ eV}$) that is at lower energies than the bandgaps of the corresponding single semiconductors, as shown in Fig. 3b. As we reported previously, the observed exciplex relaxation corresponds to the radiative recombination of electrons from the conduction band (CB) of PS with the holes present in the valence band (VB) of QDs.¹⁴

In addition to optical pumping, electronic injection (electroluminescence, EL) was also investigated by the preparation of complete LED devices based on the configuration depicted in Fig. 4a; using a compact TiO_2 layer and spiro-OMeTAD as electron and hole injecting layers, respectively.⁶

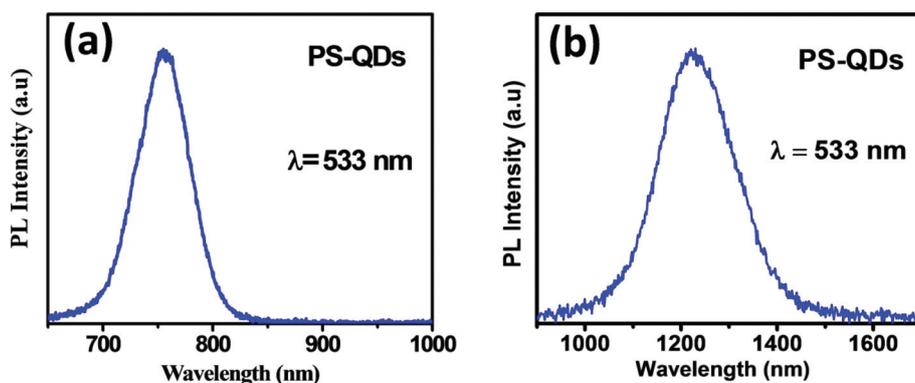


Fig. 3 Room temperature PL spectra at (a) 600–1000 nm (Si photodetector) and (b) 900–1700 nm (InGaAs photodetector) wavelength ranges of PS-QD (PbS/CdS 2.3 nm in diameter) films in which PS capped QDs were added in the solution of PS with a concentration of 300 mg ml^{-1} . The PS-QD films were spin coated at 9000 rpm and annealed at $65 \text{ }^\circ\text{C}$ for 1 minute and then at $100 \text{ }^\circ\text{C}$ for 2 minutes.

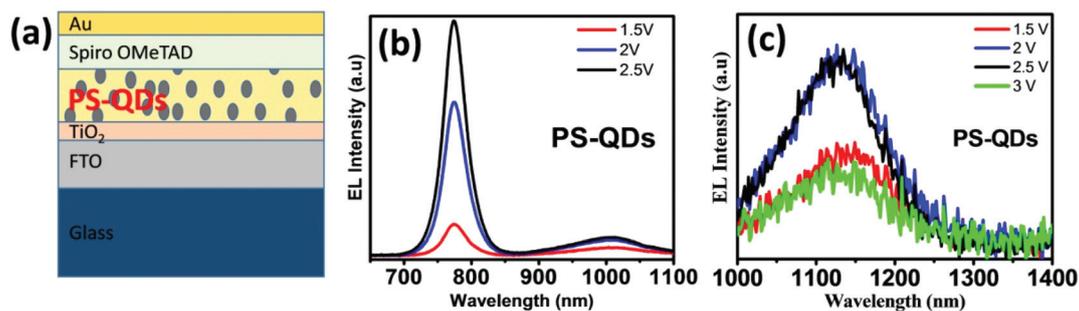


Fig. 4 (a) Schematic of the LED configuration. Electroluminescence at (b) 600–1100 nm (Si photodetector) and (c) 1000–1400 nm (InGaAs photo-detector) wavelength range of PS-QD devices at different applied voltages with PbS/CdS core/shell 2.3 nm QDs (300 mg ml^{-1}) embedded in the PS matrix. PS-QD film was spin coated at 9000 rpm and then annealed at 65°C for 1 minute and at 100°C for 2 minutes.

For the devices containing QDs, three EL emission signals that correspond to direct exciton recombination in PS and QDs (Fig. 4b) and the indirect PS-QD exciplex (Fig. 4c) are observed, respectively. Note that there is a slight shift in the exciplex peak position on comparing Fig. 4c with Fig. 3b, which arises from small variations of the QD size distributions from batch to batch syntheses. It is worth highlighting that the EL signal of the PS moiety of the PS-QD composite sample is quenched by approximately one order of magnitude (see Fig. S5, S6, and S7a†) compared to the reference sample without embedded QDs. Moreover, the QD EL intensity increases as the applied voltage increases, and this signal enhancement is even more evident at lower QD concentration (Fig. S7b†). In addition, the position of QD emission was dependent on the QD concentration in the PS-QD solution; more specifically the quenching of PS emission is expected from the type II junction, as already reported in our previous study based on PS-QD bilayers (Fig. S8†),¹⁴ which in turn promotes the origin of the exciplex state (Fig. 4c).

Finally, the samples prepared with embedded single core PbS QDs are compared to those devices prepared with PbS/CdS core/shell QDs (see Fig. S9†). Briefly, the OA ligands of the PbS core were exchanged with a PS shell, following the same procedures as for the PbS/CdS core/shell QDs (including the concentration of these QDs in the solution of PS). In agreement with our previous work,²⁷ the CdS shell induces a notable enhancement of the EL signal, not only from the QDs but also from the PS, as one would expect from the efficient passivation of the surface states (Fig. S9†).

In summary, we have developed a new method for producing PS layers with embedded core and core/shell QDs that yield highly homogeneous, low roughness and pinhole free PS-QD composite films. The introduction of embedded QDs has a dramatic effect on the perovskite crystal grains, whose size is enlarged by 4–5 fold, compared to the reference samples without QDs; it is worth mentioning that the crystal size measured for PS-QD films is in the same order of magnitude as the overall layer thickness. Very importantly, the strong interaction between PS and the embedded QDs promotes the emission from the PS-QD exciplex; therefore, our approach

constitutes a valuable proof of concept on the coupling of these two important families of materials. In particular, exploiting our methodology and device configuration constitutes a suitable tool for producing intimately packed films, where the interaction between PS and QDs can be induced and monitored by applying both optical pumping and electrical injection. The development of high quality layers and devices that not only show optical but also electrically induced exciplex states opens up a highly interesting scenario for the development of new and advanced optoelectronic devices from wavelength tunable LEDs to intermediate bandgap solar cells.

Acknowledgements

This work was supported by Generalitat Valenciana (projects PROMETEOII/2014/020, PROMETEOII/2014/059, and ISIC/2012/008) and Spanish MINECO (Ministry of Economy and Competitiveness) under projects MAT2013-47192-C3-1-R, MAT2015-70611-ERC and TEC2014-53727-C2-1-R. T. T. N. thanks Spanish MINECO for her scholarship.

References

- 1 http://www.nrel.gov/ncpv/images/efficiency_chart.jpg.
- 2 A. Kojima, K. Teshima, Y. Shirai and T. Miyasaka, *J. Am. Chem. Soc.*, 2009, **131**, 6050–6051.
- 3 W. Tress, N. Marinova, O. Inganäs, M. K. Nazeeruddin, S. M. Zakeeruddin and M. Graetzel, *Adv. Energy Mater.*, 2015, **5**, 1400812.
- 4 D. Bi, W. Tress, M. I. Dar, P. Gao, J. Luo, C. Renevier, K. Schenk, A. Abate, F. Giordano, J.-P. Correa Baena, J.-D. Decoppet, S. M. Zakeeruddin, M. K. Nazeeruddin, M. Grätzel and A. Hagfeldt, *Sci. Adv.*, 2016, **2**, e1501170.
- 5 B. R. Sutherland and E. H. Sargent, *Nat. Photonics*, 2016, **10**, 295–302.
- 6 O. A. Jaramillo-Quintero, R. S. Sanchez, M. Rincon and I. Mora-Sero, *J. Phys. Chem. Lett.*, 2015, **6**, 1883–1890.

- 7 Z.-K. Tan, R. S. Moghaddam, M. L. Lai, P. Docampo, R. Higler, F. Deschler, M. Price, A. Sadhanala, L. M. Pazos, D. Credgington, F. Hanusch, T. Bein, H. J. Snaith and R. H. Friend, *Nat. Nanotechnol.*, 2014, **9**, 687–692.
- 8 H. Cho, S.-H. Jeong, M.-H. Park, Y.-H. Kim, C. Wolf, C.-L. Lee, J. H. Heo, A. Sadhanala, N. Myoung, S. Yoo, S. H. Im, R. H. Friend and T.-W. Lee, *Science*, 2015, **350**, 1222–1225.
- 9 I. Suárez, E. J. Juárez-Pérez, J. Bisquert, I. Mora-Seró and J. P. Martínez-Pastor, *Adv. Mater.*, 2015, **27**, 6157–6162.
- 10 G. Xing, N. Mathews, S. S. Lim, N. Yantara, X. Liu, D. Sabba, M. Grätzel, S. Mhaisalkar and T. C. Sum, *Nat. Mater.*, 2014, **13**, 476–480.
- 11 F. Deschler, M. Price, S. Pathak, L. E. Klintberg, D.-D. Jarausch, R. Higler, S. Hüttner, T. Leijtens, S. D. Stranks, H. J. Snaith, M. Atatüre, R. T. Phillips and R. H. Friend, *J. Phys. Chem. Lett.*, 2014, **5**, 1421–1426.
- 12 H. Zhu, Y. Fu, F. Meng, X. Wu, Z. Gong, Q. Ding, M. V. Gustafsson, M. T. Trinh, S. Jin and X. Y. Zhu, *Nat. Mater.*, 2015, **14**, 636–642.
- 13 Z. Ning, X. Gong, R. Comin, G. Walters, F. Fan, O. Voznyy, E. Yassitepe, A. Buin, S. Hoogland and E. H. Sargent, *Nature*, 2015, **523**, 324–328.
- 14 R. S. Sanchez, M. S. de la Fuente, I. Suarez, G. Muñoz-Matutano, J. P. Martinez-Pastor and I. Mora-Sero, *Sci. Adv.*, 2016, **2**, e1501104.
- 15 P. V. Kamat, *J. Phys. Chem. C*, 2008, **112**, 18737–18753.
- 16 S. A. McDonald, G. Konstantatos, S. Zhang, P. W. Cyr, E. J. D. Klem, L. Levina and E. H. Sargent, *Nat. Mater.*, 2005, **4**, 138–142.
- 17 A. J. Nozik, M. C. Beard, J. M. Luther, M. Law, R. J. Ellingson and J. C. Johnson, *Chem. Rev.*, 2010, **110**, 6873–6890.
- 18 G. H. Carey, A. L. Abdelhady, Z. Ning, S. M. Thon, O. M. Bakr and E. H. Sargent, *Chem. Rev.*, 2015, **115**, 12732–12763.
- 19 Z. Yang, A. Janmohamed, X. Lan, F. P. García de Arquer, O. Voznyy, E. Yassitepe, G.-H. Kim, Z. Ning, X. Gong, R. Comin and E. H. Sargent, *Nano Lett.*, 2015, **15**, 7539–7543.
- 20 D. N. Dirin, S. Dreyfuss, M. I. Bodnarchuk, G. Nedelcu, P. Papagiorgis, G. Itskos and M. V. Kovalenko, *J. Am. Chem. Soc.*, 2014, **136**, 6550–6553.
- 21 G. Seo, J. Seo, S. Ryu, W. Yin, T. K. Ahn and S. I. Seok, *J. Phys. Chem. Lett.*, 2014, **5**, 2015–2020.
- 22 L. Etgar, P. Gao, P. Qin, M. Graetzel and M. K. Nazeeruddin, *J. Mater. Chem. A*, 2014, **2**, 11586–11590.
- 23 L. Hu, W. Wang, H. Liu, J. Peng, H. Cao, G. Shao, Z. Xia, W. Ma and J. Tang, *J. Mater. Chem. A*, 2015, **3**, 515–518.
- 24 X. Gong, Z. Yang, G. Walters, R. Comin, Z. Ning, E. Beauregard, V. Adinolfi, O. Voznyy and E. H. Sargent, *Nat. Photonics*, 2016, **10**, 253–257.
- 25 S.-S. Li, C.-H. Chang, Y.-C. Wang, C.-W. Lin, D.-Y. Wang, J.-C. Lin, C.-C. Chen, H.-S. Sheu, H.-C. Chia, W.-R. Wu, U. S. Jeng, C.-T. Liang, R. Sankar, F.-C. Chou and C.-W. Chen, *Energy Environ. Sci.*, 2016, **9**, 1282–1289.
- 26 V. D’Innocenzo, A. R. Srimath Kandada, M. De Bastiani, M. Gandini and A. Petrozza, *J. Am. Chem. Soc.*, 2014, **136**, 17730–17733.
- 27 R. S. Sanchez, E. Binetti, J. A. Torre, G. Garcia-Belmonte, M. Striccoli and I. Mora-Sero, *Nanoscale*, 2014, **6**, 8551–8555.